



Core cross-linked hyaluronan-styrylpyridinium micelles as a novel carrier for paclitaxel

Youhua Tao^a, Jing Xu^b, Mingqing Chen^b, Huiyu Bai^b, Xiaoya Liu^{b,*}

^a Department of Biomedical Sciences Texas Tech University Health Sciences Center, Paul L. Foster School of Medicine, El Paso, TX 79905, USA

^b School of Chemical and Material Engineering, Jiangnan University, Wuxi 214122, PR China

ARTICLE INFO

Article history:

Received 18 July 2011

Received in revised form

22 November 2011

Accepted 23 November 2011

Available online 6 December 2011

Keywords:

Hyaluronan

Cross-linked polymeric micelles

Drug delivery

Paclitaxel

ABSTRACT

In this study, cross-linked hyaluronan-styrylpyridinium (HA-SbQ) micelles were prepared to be used as a novel carrier for paclitaxel (PTX). PTX was successfully encapsulated into the hydrophobic cores of the cross-linked micelles using the dialysis method. The resultant PTX-loaded cross-linked HA-SbQ micelles were about 113 nm in diameter with spherical shape and high encapsulation efficiency. Fluorescence microscopy and high-performance liquid chromatography studies showed that PTX-loaded cross-linked HA-SbQ micelles had excellent cellular uptake ability by bone marrow derived macrophages (BMM) and human glioma U87 cells. Cellular uptake of cross-linked HA-SbQ micelles was found to be higher than that of un-cross-linked ones due to smaller size and more stable structure. In vitro cytotoxicity studies also revealed that the PTX-loaded cross-linked micelles were more potent than those of PTX-loaded un-cross-linked micelles and free PTX. These results suggested that cross-linked HA-SbQ micelles could be a potential vehicle for delivering hydrophobic chemotherapeutic drugs to tumors.

© 2011 Elsevier Ltd. All rights reserved.

1. Introduction

Polymeric micelles formed by self-assembly of amphiphilic block copolymers in aqueous solution have received widespread attention in the past decade (Deng, Li, Yao, He, & Huang, 2010; Guo & Jiang, 2009; Harada & Kataoka, 1999; Jenekhe & Chen, 1998; Liu et al., 2011; Matsumura & Kataoka, 2009; Nishiyama & Kataoka, 2006; O'Reilly, Hawker, & Wooley, 2006; Tao et al., 2009; Wang et al., 2011). Polymeric micelles have a unique core-shell structure which not only enables the system to incorporate poorly soluble drugs but also protects drugs from inactivation in biological media. Due to their small particle size, these systems exhibit many advantages such as targeting ability, long circulation and easy production of effective delivery systems (Chan et al., 2009; Huo, Zhang, Zhou, Zou, & Li, 2011; Li et al., 2011; Torchilin, 2001; Valencia et al., 2011). Polymeric micelles are therefore considered to be an excellent delivery system for hydrophobic anti-cancer drugs. However, one remaining practical challenge for micellar drugs is their inferior in vivo stability (Bae & Yin, 2008). In the past several years, various cross-linking approaches have been adopted to improve micellar stability (O'Reilly et al., 2006; Rijcken, Soga, Hennink, & Nostrum, 2007). The cross-linking of micelles could take place on the hydrophilic shell (Cheng, Khoshdel, & Wooley, 2007), within the hydrophobic core (Li et al., 2009; Talelli et al., 2010), or at the

core-shell interface (Xu, Meng, Cheng, & Zhong, 2009). However, there are only a few reports on the development of cross-linked micelles for anticancer drug delivery (Abdullah Al, Lee, Lee, Lee, & Park, 2011; Talelli et al., 2011; Tao, Liu, Chen, Yang, & Liu, 2012; Xiong et al., 2011).

Hyaluronan (also named hyaluronate, hyaluronic acid or HA) is a naturally occurring polysaccharide originally extracted from bovine vitreous humour, rooster combs or umbilical cords (Rinaudo, 2011), and now has been successfully produced on a large scale by *Streptococcus* bacteria in high purity and good yield (Gao, Du, & Chen, 2006; Ogradowski, Hokka, & Santana, 2005). It consists of repeating β -(1 \rightarrow 4)-D-glucuronic acid β -(1 \rightarrow 3)-N-acetyl-D-glucosamine disaccharide units (Chytil, Strand, Christensen, & Pekar, 2011; Chytil & Pekar, 2009) (Fig. 1a). Since it is a biopolymer, much current interest focuses on its applications in biomedicine and pharmaceuticals (Lee, Lee, & Park, 2008; Lee, Ahn, & Park, 2009; Pitarresi, Pierro, Palumbo, Tripodo, & Giammona, 2006).

Paclitaxel is known to have highly effective activity against various tumors and has been used clinically in the treatment of metastatic breast cancer, ovarian cancer and several other malignancies. Because the water solubility of PTX is very low, the commercial preparation of PTX is formulated in a solution composed of a 50:50 (v/v) mixture of Cremophor EL (polyethoxylated castor oil) and dehydrated alcohol, which is diluted 5–20 fold in normal saline or dextrose solution (5%) before administration. However, the use of Cremophor EL causes serious side effects such as nephrotoxicity, neurotoxicity and cardiotoxicity. These serious side effects have limited the clinical application

* Corresponding author. Tel.: +86 510 85917763.

E-mail address: lx@jiangnan.edu.cn (X. Liu).

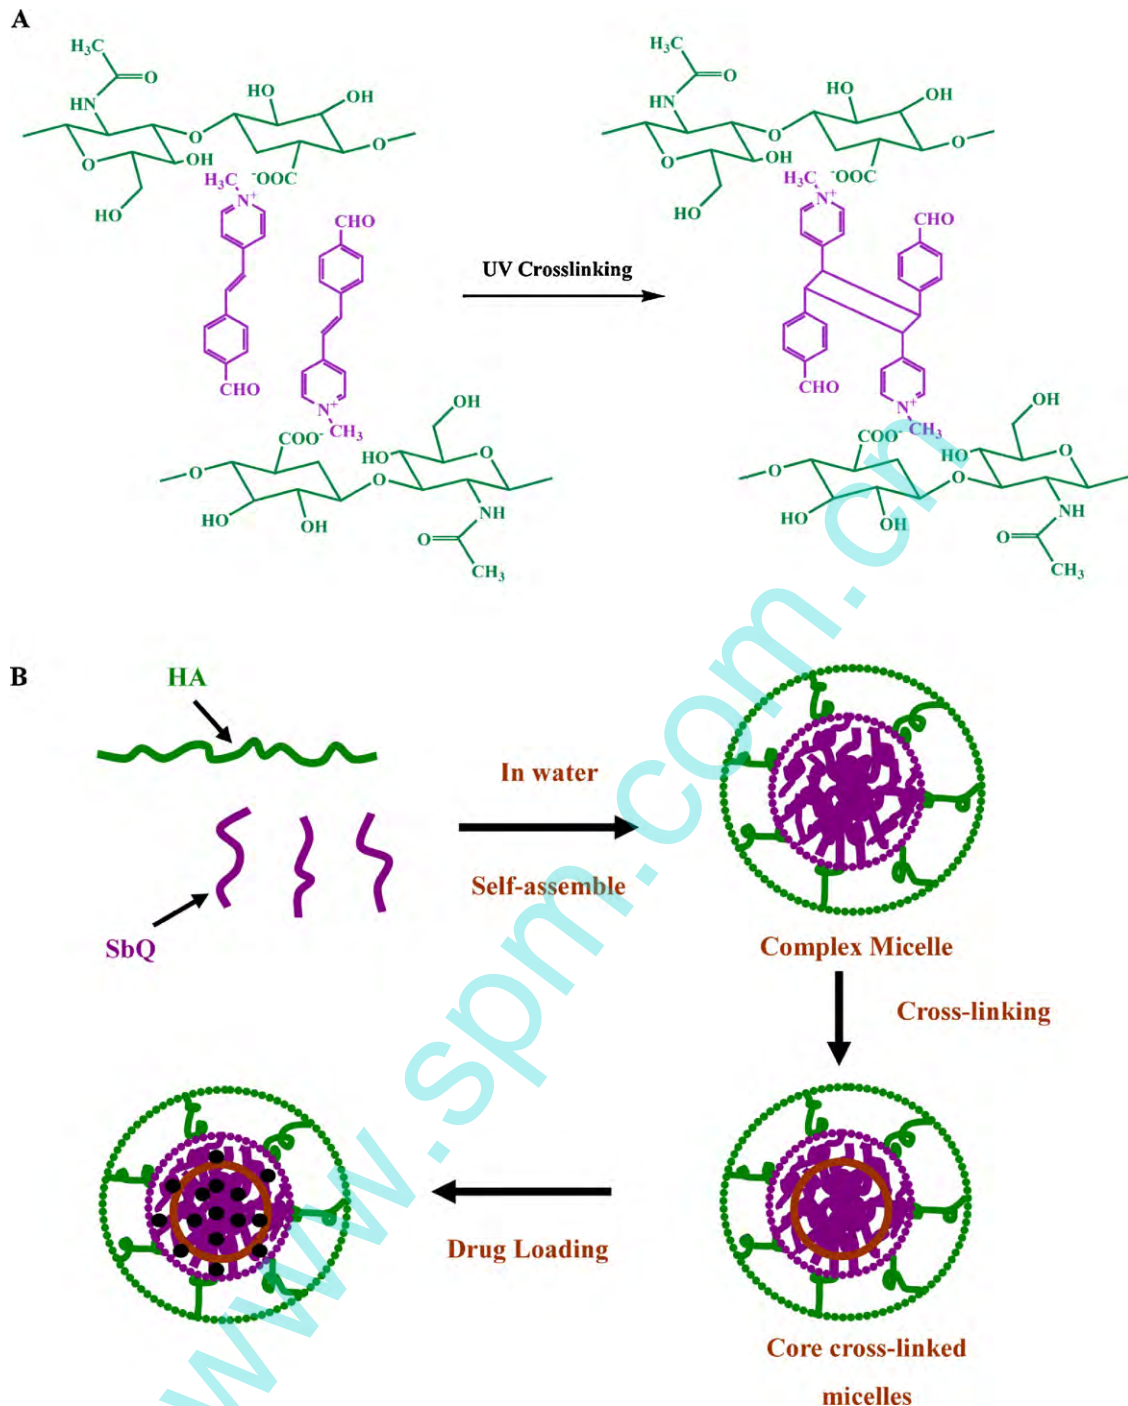


Fig. 1. (A) Chemical structure of HA and SbQ. (B) Schematic illustration of micelle formation, cross-linking and drug loading.

of Taxol[®] and caused lots of inconvenience when it was clinical applied. Therefore, it is emergent to find a drug delivery system for paclitaxel without Cremophor EL. In recent years, several drug delivery systems, such as polymeric micelles (Yao, Zhang, Ping, & Yu, 2007; Zhang et al., 2005; Zhang et al., 2008), liposomes and amphiphilic nanoparticles (Bilensoy, Gurkaynak, Dogan, & Hincal, 2008), have been studied to increase solubility of paclitaxel and to minimize the side effects of the formulation, among these new delivery vehicles, polymeric micelles have attracted an increasing interest.

We have previously reported the complex micelles formation between a negatively charged hyaluronan (HA) and an oppositely charged styrylpyridinium (SbQ) in aqueous solution (Xu et al., 2011). Cross-linking of the hydrophobic core via dimerization reaction of the SbQ molecules induced by UV light ultimately produces crosslinked micelles. The purposes of present work were: (1) to encapsulate the hydrophobic anticancer drug paclitaxel into the hydrophobic cores of the cross-linked HA-SbQ micelles, (2) to evaluate the cellular uptake ability of the micelles by bone marrow derived macrophages (BMM) and human glioma U87 cells, (3) to

evaluate the cytotoxicity of both blank micelles and PTX-loaded micelles against BMM and U87 cells and (4) to compare the stability, cellular uptake and cytotoxicity of cross-linked HA-SbQ micelles and un-cross-linked ones and to show the potential of cross-linked HA-SbQ micelles as a novel carrier for anticancer drug.

2. Materials and methods

2.1. Materials

1-Methyl-4-[2-(4-formylphenyl)-ethenyl]-pyridiniummethosulphate (SbQ) was provided by SHOWA KAKO Co. Ltd. (Japan). Sodium hyaluronate (HA), with a viscosity average molecular weight of 22 kDa, was purchased from Bio Chemicals (USA). All other chemicals and solvents were of analytical grade and were used without further purification.

2.2. Preparation of PTX-loaded cross-linked HA-SbQ micelles

HA-SbQ polymeric complex micelles were prepared as described earlier (Xu et al., 2011). Briefly, a HA solution was prepared by dissolving sodium hyaluronate in water, and stirring overnight at room temperature to ensure complete dispersion. Stock solutions of SbQ were prepared by dissolving SbQ in water. The HA solutions were then mixed with SbQ solutions, ensuring the molar ratio of the positively charged SbQ and negatively charged carboxylate groups of HA was equal. To obtain cross-linked particles, the micelle solutions were irradiated under a POWER ARC UV 100 Lamp for 45 min.

PTX-loaded cross-linked HA-SbQ micelles were prepared by dialysis technique (Kim et al., 2006; Wang et al., 2008). Briefly, 0.17 mg PTX dissolved in 5 ml methanol were slowly added to 10 ml crosslinked-HA-SbQ micelles solutions (0.1 mg/ml) under stirring, and then the methanol solvent was removed by dialysis (Millipore dialysis tube, molecular weight cutoff 12–14 kDa, USA) to obtain PTX-loaded cross-linked HA-SbQ micelles. The dust and impurity in the sample solution were removed by passing through a filter (0.45 μm , Millipore). Lissamine rhodamine B 1,2-dihexadecanoyl-sn-glycero-3-phosphoethanolamine, triethylammonium salt (rDHPE; Invitrogen) was used to label cross-linked HA-SbQ micelles and appeared as red fluorescence.

2.3. Characterization of PTX-loaded cross-linked HA-SbQ micelles

Average particle size and size distribution of the micelles were measured by Malvern Zetasizer Nano ZS (Malvern, UK). The shape and surface morphology of the micelles were investigated by Atomic force microscopy (AFM), 100 μl of HA-SbQ micelle solution was placed on a clean mica surface and then air-dried overnight. The image was obtained with a Benyuan CSPM 4000 AFM system.

2.4. Determination of drug loading capability

Drug loading capability of the cross-linked HA-SbQ micelles was determined using high-performance liquid chromatography (HPLC). PTX-loaded micelles solution (50 μl) was transferred into 10 ml volumetric flask and diluted with methanol to the mark. The solution was centrifuged at 10,000 rpm for 10 min, 20 μl of supernatant was injected into the chromatographic system. The HPLC system (LC-2010C, Shimadzu, Japan) was equipped with a Lichrospher C18 column (4.6 mm \times 250 mm, 5 μm) with a mobile phase of methanol and water (75:25), the flow rate and column temperature was set at 1 ml/min and 30 $^{\circ}\text{C}$, respectively. The signals were recorded by UV detector at 227 nm. A calibration line was conducted to determination PTX concentration in the range of

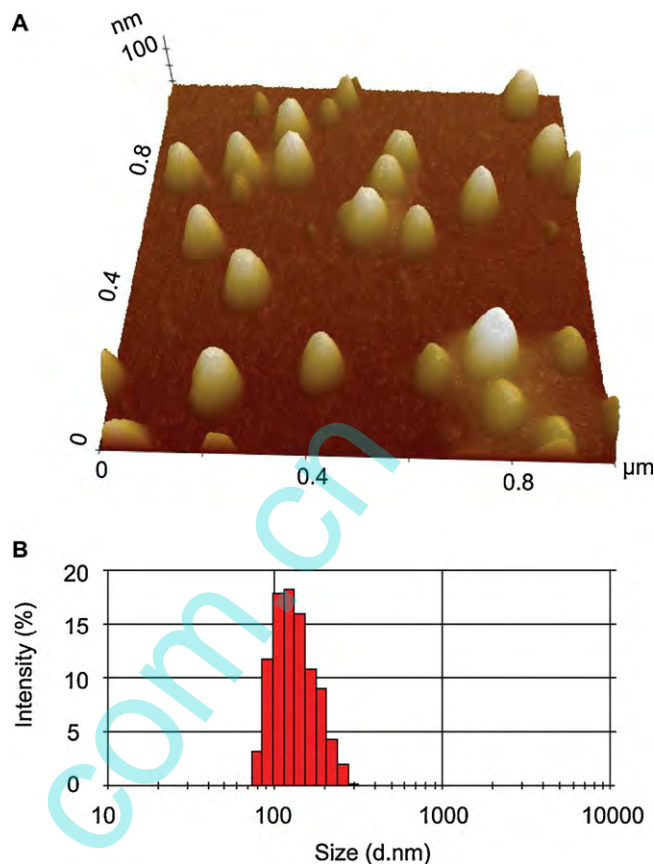


Fig. 2. AFM image (A) and the size distribution (B) of PTX-loaded cross-linked HA-SbQ micelles with a PTX-loading content of 30.1% in distilled water.

0.5–25 mg/l, and the r^2 -value of peak area against PTX concentration was at least 0.999. The encapsulation efficiency (EE, %) and the drug loading coefficient (DL, wt.%) were calculated based on the following formulations:

$$EE (\%) = \frac{\text{weight of PTX in micelles}}{\text{weight of the feeding PTX}} \times 100$$

$$DL (\text{wt}\%) = \frac{\text{weight of PTX in micelles}}{\text{weight of the feeding micelles and PTX}} \times 100$$

2.5. PTX releases from cross-linked HA-SbQ micelles in vitro

PTX release behavior was studied in vitro in phosphate buffered saline (PBS) solution. Briefly, the solutions of PTX-loaded cross-linked HA-SbQ micelles were respectively placed into visking dialysis tubing (molecular weight cutoff 12–14 kDa, Millipore, USA) and dialyzed against 50 ml PBS solutions with 1% Tween 80 at 37 $^{\circ}\text{C}$ in an air-bath shaker at 50 rpm. Then, 0.5 ml of the release media was collected and replaced with an equal volume of the fresh release media at predefined time intervals. The release amounts of PTX were determined by HPLC method.

2.6. Cell culture

Mice femur bone marrow was dissociated into single cell suspensions. Bone marrow cells and bone marrow derived macrophages (BMM) were cultured with DMEM with fetal bovine serum, 1% glutamine, 10 mg/ml ciprofloxacin, and 500 U/ml macrophage colony stimulating factor (MCSF). Human glioma U87 cells labeled with green fluorescence were obtained from

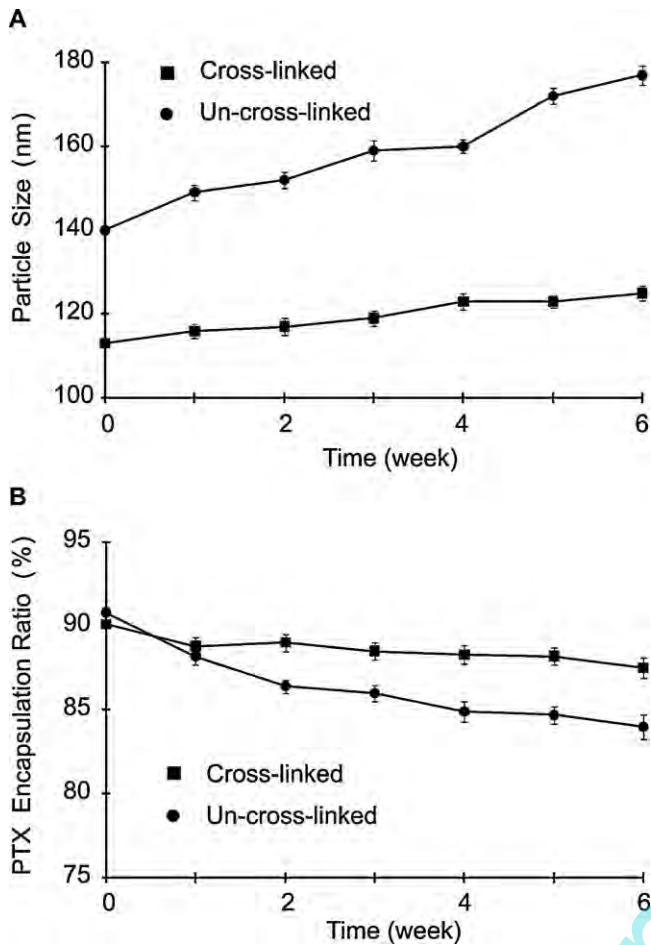


Fig. 3. PTX-loaded HA-SbQ micelles storage stability. (A) Micelles size as a function of time. (B) PTX encapsulation ratio as a function of time.

American Type Culture Collection (ATCC). For the MTT assay, cells were plated on 96-well plates to confluence and were allowed to adhere overnight.

2.7. Fluorescence microscopy

The rDHPE-labeled HA-SbQ micelles exhibited a red fluorescence. Images were captured using a Nikon TE2000-U (Nikon Instruments Inc., Melville, NY) with a swept-field confocal

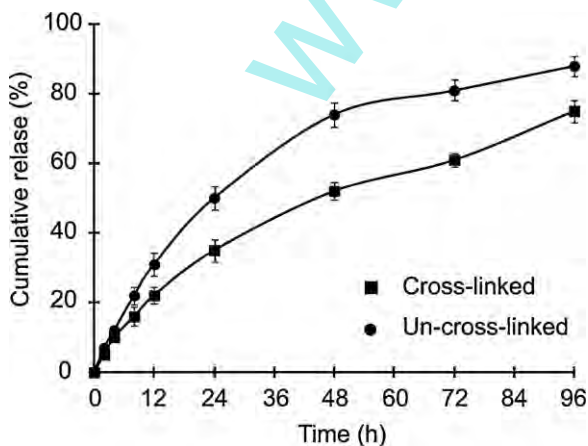


Fig. 4. PTX release profiles in PBS solutions with 1% Tween 80 at 37 °C. The micelles concentration was 0.1 mg/mL.

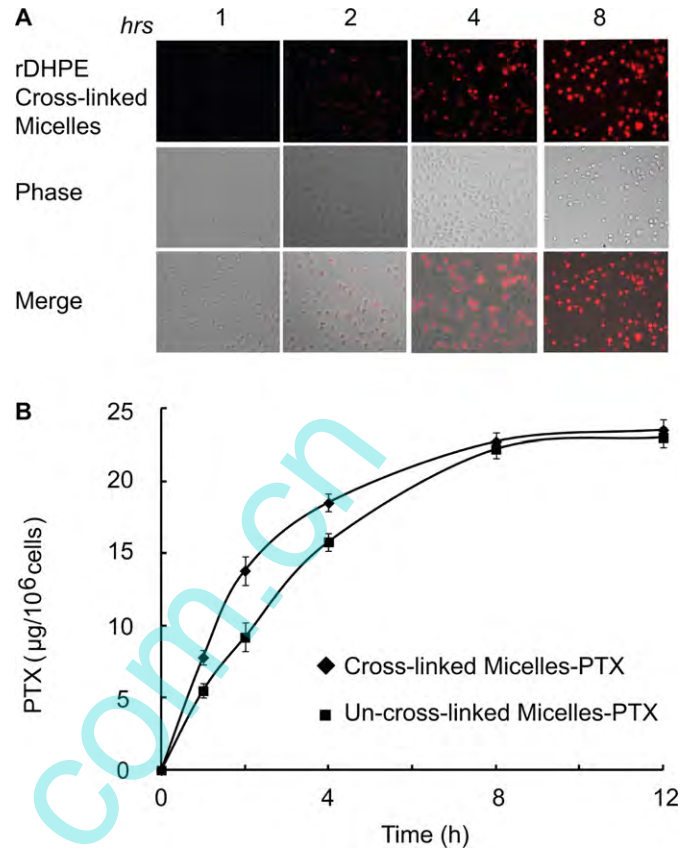


Fig. 5. HA-SbQ micelles uptake by BMM cell. (A) Fluorescent microscopy of BMM cell treated with 100 μM rDHPE-labeled cross-linked HA-SbQ micelles. (B) To confirm intracellular drug levels, cell lysates of cultured BMM treated with 100 μM of micelles were collected at specified times and assayed by HPLC.

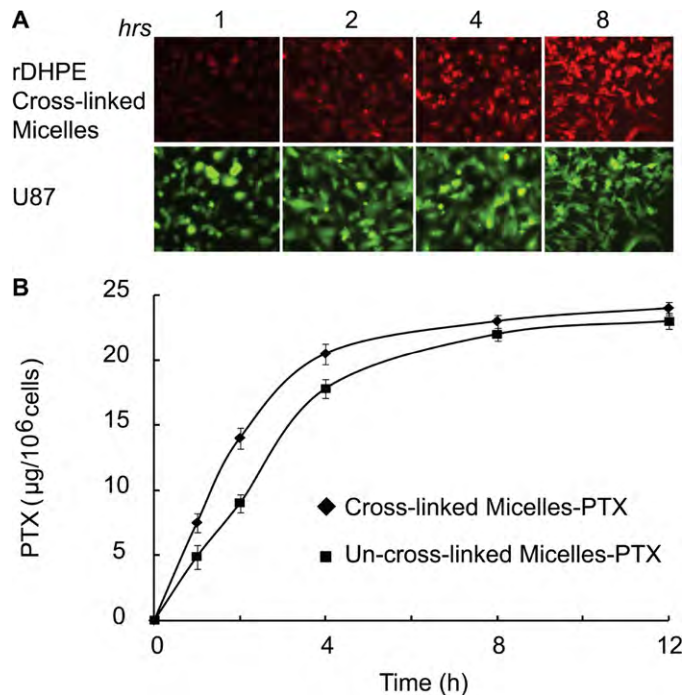


Fig. 6. HA-SbQ micelles uptake by U87 cell. (A) Fluorescent microscopy of U87 cell treated with 100 μM rDHPE-labeled cross-linked HA-SbQ micelles. (B) To confirm intracellular drug levels, cell lysates of cultured U87 treated with 100 μM of micelles were collected at specified times and assayed by HPLC.

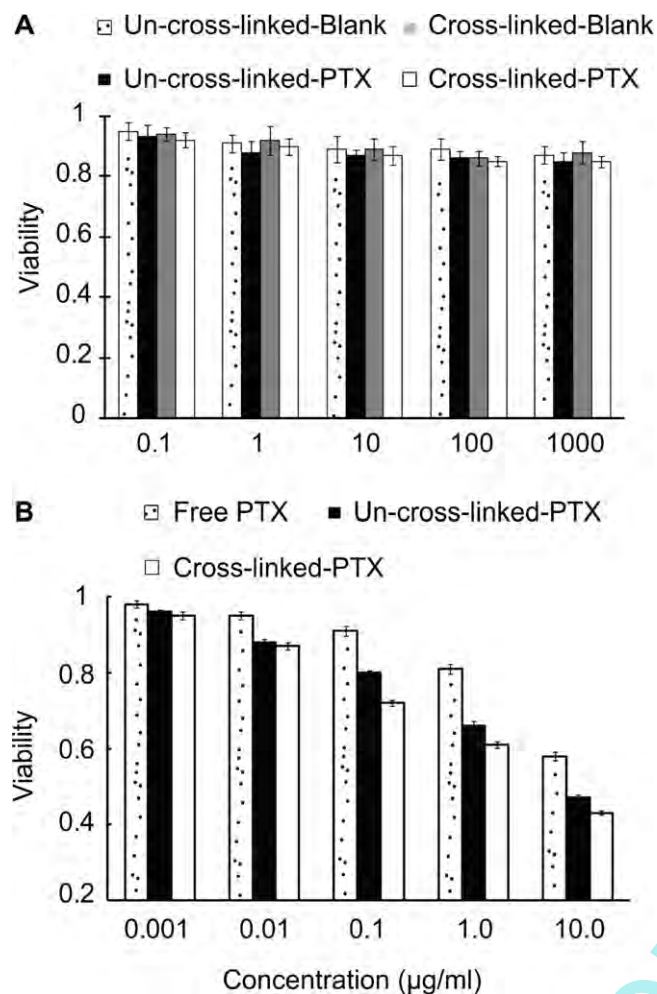


Fig. 7. Cell viability of BMM and U87 incubated with blank and PTX-loaded HA-SbQ micelles. (A) MTT cytotoxicity assay were shown no toxicity to BMM at higher concentration of blank and PTX-loaded HA-SbQ micelles. (B) In vitro cytotoxicity of various formulations of PTX against U87 cell. 12 h incubation then washout following fresh medium, MTT analysis of chemosensitivities was performed at day 3.

microscope, 488 nm (green) and 568 nm (red) laser excitations, and a 20× objective.

2.8. Cell viability assays

U87 and BMM cell viability was determined using the MTT assay. MTT reduction was measured in U87 and BMM with PTX concentration ranging from 0.001 to 1000 µg/ml for 12 h and then washed out by fresh media. The assay was based on the ability of active mitochondrial dehydrogenase to convert dissolved MTT to water-insoluble purple formazan crystals. To each BMM or U87 containing well in a 96-well plate, 100 µl of MTT solution [5 mg/ml solution in 10% fetal bovine serum (FBS) in phosphate buffered saline (PBS)] was added and incubated for 4 h at 37 °C. At the end of the incubation period, the media was replaced with 100 µl of dimethyl sphingosine (DMSO) for 15 min at room temperature and absorbance at 490 nm was determined using an ELISA plate reader.

3. Results

3.1. Preparation and characterization of PTX-loaded cross-linked HA-SbQ micelles

Our previous work showed that negatively charged hyaluronan (HA) and an oppositely charged styrylpyridinium species (SbQ)

could form nano-sized micelles with a core-shell structure composed of a hydrophobic SbQ core and a hydrophilic HA shell layer (Xu et al., 2011). Cross-linking of the hydrophobic core via dimerization reaction of the SbQ molecules induced by UV light ultimately produces crosslinked micelles (Fig. 1). The anticancer drug, paclitaxel (PTX), is known to have the highly hydrophobic property, so that we hope to use cross-linked HA-SbQ micelles as a carrier for PTX to increase its aqueous solubility. The dialysis method was used to prepare PTX-loaded cross-linked HA-SbQ micelles in this study. PTX dissolved in methanol was first added to the nanoparticle solution, and then was dialyzed against aqueous medium. In the dialysis process, methanol was gradually removed, which resulted that PTX spontaneously transferred from the aqueous medium into the hydrophobic cores of the micelles due to the driving force of hydrophobic interaction. AFM was employed to visualize micelles morphology. AFM image (Fig. 2a) shows that PTX-loaded cross-linked HA-SbQ micelles were still spherical in shape. The size distribution of the micelles was unimodal (Fig. 2b), also indicating the formation of the expected monodispersed micelles.

The physicochemical characterization and drug-loading parameters of PTX-loaded cross-linked HA-SbQ micelles are summarized in Table 1. The amount of PTX (i.e., 10 mg) was kept constant, and concentration of HA-SbQ was varied accordingly (i.e., 20, 30, 50 mg). Formulation of 1/3 (drug/carrier) was found to be appropriate with particle size of 113 ± 3.5 nm, drug loading coefficient of $30.1 \pm 1.9\%$ and encapsulation ratio of $90.1 \pm 1.0\%$, respectively. The zeta potential of PTX-loaded cross-linked HA-SbQ micelles also shown in Table 1 indicated the negative charges on the micelles surface.

The conventional micelle drug delivery systems based on the linear amphiphilic copolymers suffer from instability because micelles tend to disassemble in vivo. Maintaining the dimensional stability of micelles is crucial for many applications (Kim, Sahay, Kabanov, & Bronich, 2010; Abdullah Al et al., 2011). Cross-linking may improve stability of the micelles. Fig. 3 shows the particle size and drug content of PTX-loaded cross-linked HA-SbQ micelles and un-cross-linked ones. As shown in Fig. 3, un-cross-linked micelles showed obvious change on size and drug content in 6 weeks, exhibiting poor storage stability, whereas the cross-linked micelles showed insignificant change in 6 weeks, demonstrating that the cross-linked HA-SbQ-PTX micelles have good storage during this time period.

3.2. In vitro drug release study

PTX release behavior from cross-linked HA-SbQ-PTX micelles was studied in vitro in PBS solution with 1% Tween 80 at 37 °C. The cumulative PTX release profiles are shown in Fig. 4. Only 35% PTX released from cross-linked HA-SbQ-PTX micelles within 24 h, and approximately 75% PTX was released during 96 h. This result showed that the micelle carrier can not only solubilize the poorly soluble drugs, but also sustain PTX release. More interestingly, the release of PTX from cross-linked HA-SbQ-PTX micelles was significantly inhibited, compared with those un-cross-linked controls. The suppression in release of PTX was also attributed to the cross-linking, which restricted the mobility of PTX, consequently, its release became slower.

3.3. In vitro cellular uptake of micelles

The cellular uptake of HA-SbQ micelles was examined to demonstrate the penetration of the micelles into the cells. The micelles were tested for cell uptake at a constant concentration of 100 µM. As shown in Figs. 5A and 6A, representative images reveal increasing intensity of the fluorescence signal of rDHPE-labeled cross-linked micelles, demonstrating uptake by BMM and U87 cell

Table 1

Characteristics of the PTX-loaded cross-linked HA-SbQ micelles: particle size, size distribution, drug loading coefficient and encapsulation efficiency.

Drug/carrier ^a (w/w)	Particle size ^b (nm)	Polydispersity index ^b	Zeta potential (mv)	Drug loading coefficient (%)	Encapsulation ratio (%)
1:5	83 ± 4.1	0.332 ± 0.04	-14.8 ± 0.7	17.8 ± 1.2	94.8 ± 1.2
1:4	96 ± 2.5	0.218 ± 0.03	-13.2 ± 0.4	23.3 ± 0.9	92.3 ± 0.9
1:3	113 ± 3.5	0.206 ± 0.06	-15.1 ± 0.6	30.1 ± 1.9	90.1 ± 1.0
1:2	125 ± 4.8	0.311 ± 0.06	-14.2 ± 0.8	35.1 ± 1.1	72.1 ± 1.1

^a The weight ratio of PTX to HA-SbQ micelles.^b The size and size distribution of PTX-loaded cross-linked HA-SbQ micelles determined by DLS. Data represent mean ± SE, n = 3.

over the 8-h time period. Cross-linked micelles entered BMM and U87 cell within 1 h of incubation. At 4 h, more than 50% of BMM and U87 cell contained varying levels of micelles and increased to 95% by 8 h. HPLC analysis provides quantitative information about the uptake status of micelles. As shown in Figs. 5B and 6B, the uptake of HA-SbQ micelles into BMM and U87 cells was also a time-dependent process which increased with time. The PTX delivered by cross-linked micelles accumulated within the BMM and U87 cells at a faster rate and to larger extent than that by un-cross-linked micelles. Taken together, for PTX-loaded cross-linked HA-SbQ micelles, the smaller size and stable structure may facilitate the cellular uptake, resulting in higher cellular uptake.

3.4. Toxicity

We investigated PTX-loaded micelles toxicity to macrophages and tumor cells. BMM (Fig. 7A) and U87 (Fig. 7B) were treated with varying concentrations of micelles-blank, micelles-PTX and free PTX and cell viability was measured by MTT assay at post treatment day 3. We found no significant toxicity to BMM for micelles-blank, micelles-PTX under experimental dosages, no matter whether micelles were cross-linked or not (Fig. 7A). The results also suggest that HA-SbQ micelles carrier had limited toxicity to macrophages as well as lower bio-toxicity.

Furthermore, it is shown from Fig. 7B that free PTX and PTX-loaded HA-SbQ micelles were specifically toxic to U87 cells at concentrations from 10⁻² to 10⁻⁶ mg/ml. Chemosensitivity of PTX and PTX-loaded un-cross-linked micelles and PTX-loaded cross-linked micelles was compared. As shown in Fig. 7B, PTX-loaded un-cross-linked micelles, cross-linked micelles displayed increasing cytotoxicity as the concentration increased, PTX-loaded cross-linked HA-SbQ micelles exhibited higher cytotoxicity than un-cross-linked ones and free PTX at identical concentration. The superior cytotoxicity of PTX-loaded cross-linked HA-SbQ micelles might be attributed to higher cellular uptake.

4. Conclusions

In summary, we successfully prepared cross-linked HA-SbQ micelles filled with PTX, and confirmed sustained release for PTX from micelles. Fluorescence microscopy and HPLC studies showed that PTX-loaded cross-linked HA-SbQ micelles had excellent cellular uptake ability by BMM and U87 cells. Cellular uptake of cross-linked HA-SbQ micelles was found to be higher than that of un-cross-linked ones due to smaller size and more stable structure. In vitro cytotoxicity studies also revealed that the PTX-loaded cross-linked micelles were more potent than those of PTX-loaded un-cross-linked micelles and free PTX. Taken together, cross-linked HA-SbQ micelles seem to be a potential drug delivery system of PTX for cancer chemotherapy.

Acknowledgement

This work was supported by National Natural Science Foundation of China (Grant no. 50673038).

References

- Abdullah Al, N., Lee, H., Lee, Y. S., Lee, K. D., & Park, S. Y. (2011). Development of disulfide core-crosslinked pluronic nanoparticles as an effective anticancer drug-delivery system. *Macromolecular Bioscience*, 11(9), 1264–1271.
- Bae, Y. H., & Yin, H. (2008). Stability issues of polymeric micelles. *Journal of Controlled Release*, 131(1), 2–4.
- Bilensoy, E., Gurkaynak, O., Dogan, A. L., & Hincal, A. A. (2008). Safety and efficacy of amphiphilic beta-cyclodextrin nanoparticles for paclitaxel delivery? *International Journal of Pharmaceutics*, 347(1–2), 163–170.
- Chan, J. M., Zhang, L. F., Yuet, K. P., Liao, G., Rhee, J. W., Langer, R., et al. (2009). PLGA–lecithin–PEG core–shell nanoparticles for controlled drug delivery. *Biomaterials*, 30(8), 1627–1634.
- Cheng, C., Khoshdel, E., & Wooley, K. L. (2007). One-pot tandem synthesis of a core–shell brush copolymer from small molecule reactants by ring-opening metathesis and reversible addition–fragmentation chain transfer (co)polymerizations. *Macromolecules*, 40(7), 2289–2292.
- Chytil, M., & Pekar, M. (2009). Effect of new hydrophobic modification of hyaluronan on its solution properties: Evaluation of self-aggregation. *Carbohydrate Polymers*, 76(3), 443–448.
- Chytil, M., Strand, S., Christensen, B. E., & Pekar, M. (2011). Calorimetric and light scattering study of interactions and macromolecular properties of native and hydrophobically modified hyaluronan. *Carbohydrate Polymers*, 81(4), 855–863.
- Deng, W., Li, J. A., Yao, P., He, F., & Huang, C. (2010). Green preparation process, characterization and antitumor effects of doxorubicin–BSA–dextran nanoparticles. *Macromolecular Bioscience*, 10(10), 1224–1234.
- Gao, H. J., Du, G. C., & Chen, J. (2006). Analysis of metabolic fluxes for hyaluronic acid (HA) production by *Streptococcus zooepidemicus*. *World Journal of Microbiology & Biotechnology*, 22(4), 399–408.
- Guo, M. Y., & Jiang, M. (2009). Non-covalently connected micelles (NCCMs): The origins and development of a new concept. *Soft Matter*, 5(3), 495–500.
- Harada, A., & Kataoka, K. (1999). Chain length recognition: Core–shell supramolecular assembly from oppositely charged block copolymers. *Science*, 283(5398), 65–67.
- Huo, M. R., Zhang, Y., Zhou, J. P., Zou, A. F., & Li, J. (2011). Formation, microstructure, biodistribution and absence of toxicity of polymeric micelles formed by N-octyl-N,N-carboxymethyl chitosan. *Carbohydrate Polymers*, 83(4), 1959–1969.
- Jenekhe, S. A., & Chen, X. L. (1998). Self-assembled aggregates of rod-coil block copolymers and their solubilization and encapsulation of fullerenes. *Science*, 279(5358), 1903–1907.
- Kim, J.-H., Kim, Y.-S., Kim, S., Park, J. H., Kim, K., Choi, K., et al. (2006). Hydrophobically modified glycol chitosan nanoparticles as carriers for paclitaxel. *Journal of Controlled Release*, 111(1–2), 228–234.
- Kim, J. O., Sahay, G., Kabanov, A. V., & Bronich, T. K. (2010). Polymeric micelles with ionic cores containing biodegradable cross-links for delivery of chemotherapeutic agents. *Biomacromolecules*, 11(4), 919–926.
- Lee, H., Lee, K., & Park, T. G. (2008). Hyaluronic acid–paclitaxel conjugate micelles: Synthesis, characterization, and antitumor activity. *Bioconjugate Chemistry*, 19(6), 1319–1325.
- Lee, H., Ahn, C. H., & Park, T. G. (2009). Poly[lactic-co-(glycolic acid)]-grafted hyaluronic acid copolymer micelle nanoparticles for target-specific delivery of doxorubicin. *Macromolecular Bioscience*, 9(4), 336–342.
- Li, Y. L., Zhu, L., Liu, Z. Z., Cheng, R., Meng, F. H., Cui, J. H., et al. (2009). Reversibly stabilized multifunctional dextran nanoparticles efficiently deliver doxorubicin into the nuclei of cancer cells. *Angewandte Chemie International Edition*, 48(52), 9914–9918.
- Li, X., Qian, Y., Liu, T., Hu, X., Zhang, G., You, Y., et al. (2011). Amphiphilic multiarm star block copolymer-based multifunctional unimolecular micelles for cancer targeted drug delivery and MR imaging. *Biomaterials*, 32(27), 6595–6605.
- Liu, R., Tao, Y. H., Zhu, Y., Chen, M. Q., Yang, C., & Liu, X. Y. (2011). Synthesis of double-hydrophilic poly(methylacrylic acid)–poly(ethylene glycol)–poly(methylacrylic acid) triblock copolymers and their micelle formation. *Polymer International*, 60(2), 327–332.
- Matsumura, Y., & Kataoka, K. (2009). Preclinical and clinical studies of anticancer agent-incorporating polymer micelles. *Cancer Science*, 100(4), 572–579.
- Nishiyama, N., & Kataoka, K. (2006). Current state, achievements, and future prospects of polymeric micelles as nanocarriers for drug and gene delivery. *Pharmacology & Therapeutics*, 112(3), 630–648.
- Ogrodowski, C. S., Hokka, C. O., & Santana, M. H. A. (2005). Production of hyaluronic acid by *Streptococcus*. *Applied Biochemistry and Biotechnology*, 121, 753–761.

- O'Reilly, R. K., Hawker, C. J., & Wooley, K. L. (2006). Cross-linked block copolymer micelles: Functional nanostructures of great potential and versatility. *Chemical Society Reviews*, 35, 1068–1083.
- Pitarresi, G., Pierro, P., Palumbo, F. S., Tripodo, G., & Giammona, G. (2006). Photo-cross-linked hydrogels with polysaccharide-poly(amino acid) structure: New biomaterials for pharmaceutical applications. *Biomacromolecules*, 7(4), 1302–1310.
- Rijcken, C. J. F., Soga, O., Hennink, W. E., & Nostrum, C. F. V. (2007). Triggered destabilisation of polymeric micelles and vesicles by changing polymers polarity: An attractive tool for drug delivery. *Journal of Controlled Release*, 120(3), 131–148.
- Rinaudo, M. (2011). New amphiphilic grafted copolymers based on polysaccharides. *Carbohydrate Polymers*, 83(3), 1338–1344.
- Talelli, M., Iman, M., Varkouhi, A. K., Rijcken, C. J. F., Schiffelers, R. M., Etrych, T., et al. (2010). Core-crosslinked polymeric micelles with controlled release of covalently entrapped doxorubicin. *Biomaterials*, 31(30), 7797–7804.
- Talelli, M., Rijcken, C. J. F., Oliveira, S., Van der meel, R., Van bergen en henegouwen, P. M. P., & Lammers, T. (2011). Nanobody–Shell functionalized thermosensitive core-crosslinked polymeric micelles for active drug targeting. *Journal of Controlled Release*, 151(2), 183–192.
- Tao, Y. H., Liu, X. Y., Shi, D. J., Chen, M. Q., Yang, C., & Ni, Z. B. (2009). Graftlike block copolymer bearing biodegradable epsilon-caprolactone branches: A facile route to hollow nanocages. *Journal of Physical Chemistry C*, 113(15), 6009–6013.
- Tao, Y. H., Liu, R., Chen, M. Q., Yang, C., & Liu, X. Y. (2012). Cross-linked micelles of graftlike block copolymer bearing biodegradable epsilon-caprolactone branches: A novel delivery carrier for paclitaxel. *Journal of Materials Chemistry*, 22(2), 373–380.
- Torchilin, V. P. (2001). Structure and design of polymeric surfactant-based drug delivery systems? *Journal of Controlled Release*, 73(2-3), 137–172.
- Valencia, P. M., Hanewich-Hollatz, M. H., Gao, W., Karim, F., Langer, R., Karnik, R., et al. (2011). Effects of ligands with different water solubilities on self-assembly and properties of targeted nanoparticles. *Biomaterials*, 32(26), 6226–6233.
- Wang, Y. S., Jiang, Q., Li, R. S., Liu, L. L., Zhang, Q. Q., Wang, Y. M., et al. (2008). Self-assembled nanoparticles of cholesterol-modified O-carboxymethyl chitosan as a novel carrier for paclitaxel. *Nanotechnology*, 19(14).
- Wang, Y., Yang, T., Wang, X., Dai, W., Wang, J., Zhang, X., et al. (2011). Materializing sequential killing of tumor vasculature and tumor cells via targeted polymeric micelle system. *Journal of Controlled Release*, 149(3), 299–306.
- Xiong, J. A., Meng, F. H., Wang, C., Cheng, R., Liu, Z. A., & Zhong, Z. Y. (2011). Folate-conjugated crosslinked biodegradable micelles for receptor-mediated delivery of paclitaxel. *Journal of Materials Chemistry*, 21(15), 5786–5794.
- Xu, Y. M., Meng, F. H., Cheng, R., & Zhong, Z. Y. (2009). Reduction-sensitive reversibly crosslinked biodegradable micelles for triggered release of doxorubicin. *Macromolecular Bioscience*, 9(12), 1254–1261.
- Xu, J., Bai, H., Yi, C., Luo, J., Yang, C., Xia, W., et al. (2011). Self-assembly behavior between native hyaluronan and styrylpyridinium in aqueous solution. *Carbohydrate Polymers*, 86(2), 678–683.
- Yao, Z., Zhang, C., Ping, Q. N., & Yu, L. L. L. (2007). A series of novel chitosan derivatives: Synthesis, characterization and micellar solubilization of paclitaxel. *Carbohydrate Polymers*, 68(4), 781–792.
- Zhang, X. F., Li, Y. X., Chen, X. S., Wang, X. H., Xu, X. Y., Liang, Q. Z., et al. (2005). Synthesis and characterization of the paclitaxel/MPEG-PLA block copolymer conjugate. *Biomaterials*, 26(14), 2121–2128.
- Zhang, C., Qu, G., Sun, Y., Wu, X., Yao, Z., Guo, Q., et al. (2008). Pharmacokinetics, biodistribution, efficacy and safety of N-octyl-O-sulfate chitosan micelles loaded with paclitaxel. *Biomaterials*, 29(9), 1233–1241.